


Manufacturer: Quick Bauprodukte GmbH
Test requirements: Test instruction fibre concrete "Norwegian Standard"
Material / Mixture-No.: Quick fiber concrete M1
Concrete quality: C45/55
Exposure class concrete: acc. to Eurocode 2 (EC2) X0 / XC4 / XD 3 / XF4 / XA2

Article / Article-No.: Mounting-Bipo 40 without wire, with 1 trough / 220340
Concrete cover: 40 mm
Production date: 08.12.2022
Test period: 23.01.-26.01.2023

Results dimension test

Part No.	H	Vippediagonal
1	41,0	55,0
2	40,0	55,0
3	41,0	54,0
mean	40,7	54,7

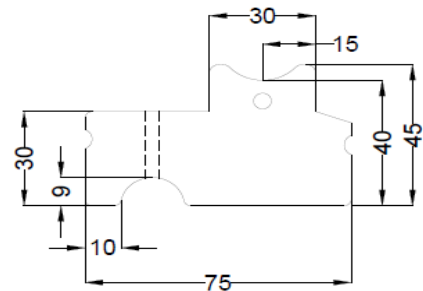

Results water absorption test

Part No.	Storage weight in g after 48 hours heat treatment curing at +105°C	Weight in g after 30 min. immersion	Water content in % after 30 min. (to be < 5 %)	Weight in g after 24 hours immersion	Water content in % after 24 hours (to be < 8,5 %)
1	178	184	3,2%	191	6,2%
2	188	194	3,2%	202	7,2%
3	186	191	2,5%	199	6,3%
mean			3,0%		6,6%

Results breaking load test

Part No.	breaking load F / kN (to be >6 kN)
1	8,2
2	8,5
3	8,0
mean	8,2

This certificate complies to the requirements of DIN / EN 10204:2005-01-3.1

The buyer is not released from any entry control.
It is also irrelevant in case of incorrect use or handling.